

A Novel Polymeric Phosphine Oxide-derived Support for Enzyme Immobilisation

William Henderson,* Helen H. Petach and Kwabena Sarfo


School of Science and Technology, University of Waikato, Private Bag 3105, Hamilton, New Zealand

Synthesis of a novel polymeric support by Mannich condensation of $P(CH_2OH)_3$ with a polyetheramine provides flexible side chains for enzyme immobilisation without loss of catalytic activity.


The immobilisation of enzymes on polymeric supports is a highly attractive method for recovering and re-using the catalysts and a wide range of supports have been used. However, there is a continued need for durable supports which are resistant to mechanical, chemical and microbial degradation, and are capable of maintaining high enzymatic activities.¹ Here we report a novel, readily synthesised polymeric phosphine oxide support for the immobilisation of enzymes, together with some preliminary results on the immobilisation and activity of immobilised urease. Related polymeric phosphine oxides are currently finding commercial application as flame retardants for cellulosic materials.²

Mannich condensation polymerisation of tris(hydroxymethyl)phosphine [generated *in situ* from tetrakis(hydroxymethyl)phosphonium chloride (THPC) and sodium hydroxide]³ with 1 equiv. (*i.e.* NH:OH = 2.0) of glyceryl poly(oxypropylene)triamine (Jeffamine T-3000) **1** proceeded in ethanol over several hours to yield the rubbery polymeric phosphine **2**. Oxidation of **2** proceeded readily on treatment with dilute aqueous hydrogen peroxide, followed by washing and drying to give the polymeric phosphine oxide **3** in 86% overall yield as a white, semi-rubbery granular solid. Scheme 1 shows the synthetic procedure employed, together with a segment of the polymer indicating the types of functional groups present. The polymer has been characterised† by elemental analyses, and by ³¹P-¹H, ¹³C-¹H, and ¹H NMR spectroscopy as a solvent-swollen gel. Thus, the ³¹P-¹H NMR spectrum of **3** showed a broad resonance ($\omega_{1/2}$ 260 Hz) at *ca.* δ 35. SEM shows the polymer to have smooth but cavitated surfaces, suggesting that the material will have significant surface area for enzyme immobilisation while minimising nonspecific adsorption.

We reasoned that the presence of the terminal long chain polyether-NH₂ groups in **3** would provide highly flexible 'anchors' for the immobilisation of enzymes, thereby minimising the reduction in activity often observed on immobilisation. Previous studies have shown that enzymes and rhodium(I) hydroformylation catalysts bound *via* short chains to the support are less active than those bound *via* longer links.⁴



Jeffamine T-3000 (**1**) $x + y + z = 50$

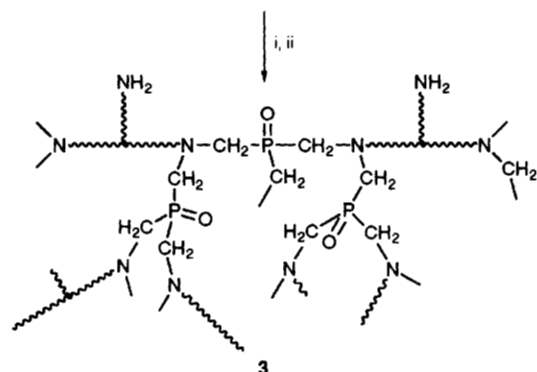

Scheme 1 Reagents and conditions: i, polymerise, EtOH; ii, H₂O₂

Accordingly, we have investigated the immobilisation of the enzyme urease onto **3** by coupling the amine groups with glutaraldehyde.

In a typical immobilisation experiment, the polymer was stirred in 5% glutaraldehyde for 1 h at 30 °C and was subsequently washed until the washings were free of glutaraldehyde. Reaction with urease (10 mg enzyme and 200 mg polymer in 5 ml phosphate buffer at pH 7.4) then proceeded for 2 h at 30 °C followed by 24 h at 4 °C. The urease-modified polymer was washed thoroughly with water and 0.1 mol dm⁻³ phosphate buffer to remove unbound urease.

Activity determinations of the immobilised urease were carried out in 0.1 mol dm⁻³ phosphate buffer at pH 7.4, 30 °C with 100 mmol dm⁻³ urea to be certain that the reaction was zero order and not dependent upon substrate concentration. Samples were removed from the reaction mixture at intervals for estimation of NH₃ by the phenol-hypochlorite method.⁵

The kinetic parameter, *K_m*, was determined from linear Lineweaver-Burk plots in which the reaction was first order in urea concentration. The polymer-immobilised urease exhibited a *K_m* of *ca.* 8 mmol dm⁻³ at pH 7.4 and 30 °C, very similar to that of the free urease (*K_m* of *ca.* 5 mmol dm⁻³). This similarity in *K_m* indicates that the environment around the immobilised enzyme is maintaining the flexibility necessary for enzyme activity and substrate accessibility to the active site. This result is in contrast to more rigid immobilisation supports which often result in a much higher *K_m* for urease, presumably due to the lack of mobility of the enzyme and inaccessibility of substrate to the active site.⁶ We believe that these results can be extended to enzymes with larger substrates (*e.g.* proteases) since penetration/diffusion limitations should be minimised owing to the long flexible anchors with which the enzymes are bound, and the smooth surface of the polymer particles (from SEM).

These poly-phosphine oxide supports are remarkably robust to changes in pH, temperature, and chemical environment. Furthermore, the described synthetic protocol can be generalised to make the synthesis of a large variety of enzyme-to-polymer 'tethers' possible. We are continuing to explore a variety of polyphosphine oxide derivatives as enzyme supports capable of stabilising catalytic activity.

We thank the University of Waikato for financial support, and Texaco Chemical Company and Albright & Wilson Ltd. for generous gifts of Jeffamine T-3000 and THPC, respectively.

Received, 31st August 1993; Com. 3/05219B

Footnote

† Polymer **3**: NMR: ³¹P-¹H (24 MHz, EtOH, external D₂O lock), δ 35 (br, $\omega_{1/2}$ *ca.* 260 Hz, LB = 1.7 Hz); ¹³C-¹H (CDCl₃, 75 MHz), δ 77-72 (m, CH₂O and CHO), and 17.5 (s, CH₃). Resonances due to the PCH₂N carbons could not be observed, though these are expected to occur at *ca.* δ 40.⁷ ¹H (CDCl₃, 300 MHz), δ 3.6 (vbr) and 1.1 (vbr).

References

- W. H. Scouten, in *Meth. Enzymol.*, ed. K. Mosbach, Academic Press, NY, 1987, **135**, 30.

- 2 E. D. Weil, in *Handbook of Organophosphorus Chemistry*, ed. R. Engel, Marcel Dekker Inc., NY, 1992, ch. 14.
- 3 A. W. Frank, D. J. Daigle, and S. L. Vail, *Text. Res. J.*, 1982, 678.
- 4 F. R. Hartley, *Supported Metal Complexes*, Kluwer Academic Publishers, Dordrecht, Holland, 1985, ch. 1.
- 5 M. W. Weatherburn, *Anal. Chem.*, 1967, **39**, 971.
- 6 B. Krajewska, M. Leszko and W. Zaborska, *J. Chem. Tech. Biotechnol.*, 1990, **48**, 337; H. Miyama, M. Kawata and Y. Nosaka, *Biotechnol. Bioeng.*, 1985, **27**, 1403; M. B. F. Martins, M. E. M. Cruz, J. M. S. Cabral and J. F. Kennedy, *J. Chem. Tech. Biotechnol.*, 1987, **39**, 201.
- 7 See e.g. A. Hohn, R. J. Geue, A. M. Sargeson and A. C. Willis, *J. Chem. Soc., Chem. Commun.*, 1989, 1644.